arXiv:cond-mat/9912254v1 [cond-mat.supr-con] 14 Dec 1999

Thermal conductivity in the vortex state of d-wave superconductors

I. Vekhter [a*] and A. Houghton [b]

[a]Department of Physics, University of Guelph, Guelph, Ontario, Canada N1G 2W1

[b]Department of Physics, Brown University, Providence, RI 02912-1843, USA

We present the results of a microscopic calculation of the longitudinal thermal conductivity of quasiparticles, κ_{xx}, in a 2D d-wave superconductor in the vortex state. Our approach takes into account both impurity scattering and a contribution to the thermal transport lifetime due to the scattering of quasiparticles off of vortices. We compare the results with the experimental measurements on high-T_c cuprates and organic superconductors.

In the last few years measurements of the thermal conductivity have become one of the most powerful probes of unconventional superconductors. Materials with linear nodes in the energy gap have been predicted to exhibit a residual linear in the temperature, T, term in κ_{xx} as $T \to 0$, which is only weakly sensitive to impurity concentration.[1] Both properties have been firmly established in the high-T_c cuprates,[2] and a linear term has been resolved in the organic superconductor κ-(BEDT-TTF)$_2$Cu(NCS)$_2$.[3]

Information on near-nodal quasiparticles can be obtained from the analysis of transport properties in the vortex state. The number of unpaired quasiparticles increases in an applied magnetic field, H,[4] and their existence leads to the sublinear, in H, increase of $\kappa_{xx}(H)$ below $T \sim 1$K.[5,6] In contrast, at higher temperatures the thermal conductivity of the cuprates has been found to decrease with the applied field, and often becomes nearly field independent above a few Tesla.[7] Recently we have proposed a unified description of both features in the cuprates.[8] In these materials the experiments are restricted to fields $H \ll H_{c2}$, while in the organic materials the entire $H - T$ range can be probed, making the analysis of $\kappa_{xx}(H,T)$ important.

We consider a clean ($l \gg \xi_0$, where l is the mean free path, and ξ_0 is the coherence length) 2-dimensional d-wave superconductor with a cylindrical Fermi surface, model the vortex lattice by an Abrikosov-like solution, and use the quasiclassical method with the approximation scheme of Ref.[9]. For $l \gg (2eH)^{-1/2} \equiv \Lambda$ the thermal conductivity is given by[8]

$$\frac{\kappa}{T} = \frac{N_0 v^2}{4\pi} \int_0^\infty \frac{d\omega}{T} \left(\frac{\omega}{T}\right)^2 \cosh^{-2}\left(\frac{\omega}{2T}\right) \times \int_0^{2\pi} d\phi \cos^2\phi \left[ReP(\widetilde{\omega})\right] \tau(\widetilde{\omega},\phi), \quad (1)$$

$$\frac{1}{2\tau(\widetilde{\omega},\phi)} = Re\sigma(\widetilde{\omega}) + 2\sqrt{\pi}\frac{\Lambda\Delta^2}{v}\frac{Re[P(\widetilde{\omega})W(u)]}{ReP(\widetilde{\omega})}\cos^2 2\phi, \quad (2)$$

where N_0 is the normal state density of states, v is the Fermi velocity, $P(\widetilde{\omega}_n) = [1 - i\sqrt{\pi}\left(2\Lambda\Delta/v\right)^2 W'(u_n)\cos^2 2\phi]^{-1/2}$, the function $W(u) = e^{-u^2}\mathrm{erfc}(-iu)$, $u_n = 2i\widetilde{\omega}_n\Lambda\mathrm{sgn}(\omega_n)/v$, the renormalized frequency $i\widetilde{\omega}_n = i\omega_n + i\sigma(i\widetilde{\omega}_n)$, depends on the self-energy due to impurity scattering, σ, and Δ is the spatial average of the amplitude of the order parameter. The second term in the effective scattering rate is due to scattering off of the vortex lattice. This term has the same symmetry as the superconducting gap, and therefore is more important at higher temperatures. At low T and H the main effect of the magnetic field is to increase the number of the excited quasiparticles near the nodes, where vortex scattering is weak; consequently the thermal conductivity increases. At higher fields

*Acknowledges the hospitality of Centre Émile Borel and Aspen Center for Physics

the number of quasiparticles is controlled by the temperature, the main effect of the vortices is to introduce a new scattering mechanism, and κ_{xx} decreases to a plateau-like feature at fields such that $v/\Lambda \geq T \gg \sigma(\omega = 0)$, in agreement with the experimental results on high-T_c cuprates.[8] The parameters of the theory are the dimensionless quantity $\delta \equiv \Lambda\Delta/v$, and the scattering rate in the normal state, Γ; the scattering phase shift is fixed to either the strong (unitarity) or the weak (Born) limit. At the mean field level $\delta = \alpha[(H_{c2} - H)/HH_{c2}]^{1/2}$ where $\alpha = (\Delta_0/\hbar v)(\hbar c/2e)^{1/2}$. For high-$T_c$ materials $\alpha \approx 2\text{-}7\mathrm{T}^{1/2}$, [8] while for κ-(BEDT-TTF)$_2$Cu(NCS)$_2$ using $\Delta_0 = 2.4$meV and $v = 5 \cdot 10^6$cm/s [3] we find $\alpha \simeq 1.3\mathrm{T}^{1/2}$.

At low T in this material $\kappa_{xx}(H)$ decreases sharply below H_{c2}.[3] In the field range $H \leq H_{c2}$ at $T = 0$ we find from Eqs.(1)-(2)

$$\frac{\kappa(H)}{\kappa_n} \approx \frac{l_{\rm eff}}{l}\frac{1}{\sqrt{1+\mu}}. \qquad (3)$$

Here κ_n is the normal state thermal conductivity, the effective mean free path $l_{\rm eff} = v/(2\sigma(\omega = 0))$, and $\mu = 4\sqrt{\pi}(l_{\rm eff}/\Lambda)\delta^2$. Near H_{c2} $\mu \propto \Delta^2 \propto H_{c2} - H$, so that $\kappa(H)/\kappa_n \approx 1 - \mu/2$ decreases linearly with field. The range over which the linear dependence holds, $\mu \ll 1$, is smaller the cleaner the sample since for $l \gg \xi_0$ we may have $\mu \geq 1$ even when $\delta \ll 1$. Consequently the linear behavior down to $0.7H_{c2}$ [3] indicates a relatively dirty sample, in agreement with the estimate of Ref.[3] which yielded $l \simeq 350$Å, or $l/\xi_0 \simeq 7$. From this estimate we obtain $\Gamma \simeq 0.4$meV; κ_{xx} determined with these parameters is shown in Fig.1.

At low T, for fields below $0.5H_{c2}$, $\kappa_{xx}(H)$ is observed to decrease with increasing field.[3] Note that the residual linear term in $\kappa_{xx}(H = 0, T)$ is only observable if $T \leq \sigma(\omega = 0)$, which is exponentially small, in Δ_0/Γ, in the Born limit. The results of Ref.[3] therefore suggest that the phase shift is close to $\pi/2$. But, in the unitarity limit $\sigma(\omega = 0) \approx \sqrt{\Gamma\Delta_0}$, and for $\Gamma \simeq 0.4$meV at low T $\kappa_{xx}(H)$ increases rather than decreases over almost the entire field range. If inelastic scattering is strong, Γ at low T and H may be much smaller than its normal state value, in which case κ_{xx} does decrease but in a narrow field range, see Fig. 1, in disagreement with experiment, suggesting that the low-field decrease is in the phonon contribution to κ_{xx}.

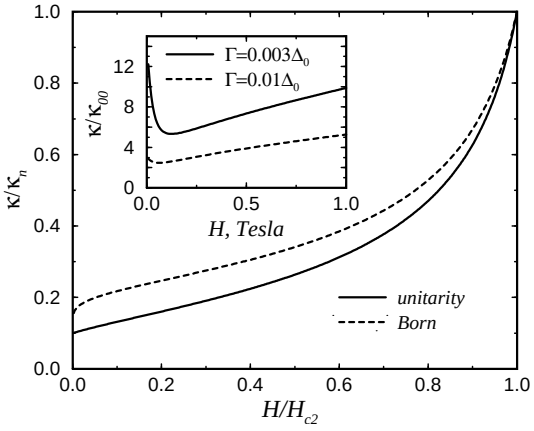

Figure 1. Field dependence of $\kappa_{xx}(H, T = 0)$ for $\Gamma = 0.15\Delta_0$, $\alpha = 1.3$, and $H_{c2} = 5$T. Inset: $T = 0.03\Delta_0$, unitarity limit. $\kappa_{00} = \pi^2 T N_0 v^2/6\Delta_0$ is the universal conductivity.[1]

Helpful discussions with K. Behnia and S. Belin are gratefully acknowledged.

REFERENCES

1. P.A.Lee, Phys. Rev. Lett. 71 (1993) 1887; M.J.Graf *et al.* Phys. Rev. B 53 (1996) 15147.
2. L. Taillefer *et al.*, Phys. Rev. Lett. 79 (1997) 483.
3. S. Belin, K. Behnia, and A. Deluzet, Phys. Rev. Lett. 81 (1998) 4728; S. Belin, Ph. D. Thesis, Universite de Paris-Sud, 1998.
4. G. E. Volovik, JETP Lett. 58 (1993), 469.
5. H. Aubin *et al.*, Phys. Rev. Lett. 82 (1999) 624; M. Chiao *et al.*, *ibid.* 82 (1999) 2943.
6. C. Kübert and P. J. Hirschfeld, Phys. Rev. Lett. 80 (1998) 4963.
7. K. Krishana *et al.* Science 277 (1997) 83.
8. I. Vekhter and A. Houghton, Phys. Rev. Lett. 83 (1999) 4626.
9. U. Brandt, W. Pesch, and L. Tewordt, Z. Phys. **201** (1967) 209.